

# Tribological behavior and cutting performance of a NbC-Ni-WC-TiC cermet

Daniela Hübler<sup>1)\*</sup>, Kristin Kropidowski<sup>2)</sup>, Dr. rer. nat. Thomas Gradt<sup>1)</sup> and Prof. Dr. h. c. Dr.-Ing. Eckart Uhlmann<sup>2)3)</sup>

<sup>1)</sup> Federal Institute for Materials Research and Testing (BAM), 12203 Berlin, Germany

<sup>2)</sup> Institute for Machine Tools and Factory Management (IWF), Technische Universität Berlin, 10587 Berlin, Germany,

<sup>3)</sup> Fraunhofer Institute for Production Systems and Design Technology (IPK), 10587 Berlin, Germany,

\*Corresponding author: daniela.huebler@bam.de

The addition of WC and TiC in a nickel bonded NbC cermet was investigated regarding the tribological behavior under dry oscillating sliding at different relative humidities  $\varphi$  and the cutting performance in dry cylindrical turning of C45E at different cutting speeds. NbC-12Ni-12WC-14TiC shows similar coefficient of friction  $f$  and wear rate compared to NbC-12Ni at  $\varphi = 2\%$ , but no pronounced decrease in  $f$  with increasing humidity. When turning C45E, NbC-12Ni-12WC-14TiC shows lower material removal  $V_w$  compared to other NbC-based cermets, which can be attributed to inhomogeneities in the cutting material and a low hardness.

**Keywords:** niobium carbide, NbC cermets, tribology, dry cylindrical turning

## 1. Introduction

Niobium carbide (NbC) is an alternative to conventional cutting materials such as tungsten carbide (WC). Several studies investigated the influence of different metal binders such as cobalt (Co), iron (Fe) and nickel (Ni) and the processing parameters on the microstructure and mechanical properties of NbC-based cermets [1,2]. In contrast to WC-based tools, during dry turning, the potential of NbC-based tools develops with increasing cutting speed  $v_c$  through increasing process stability. This study aims to investigate the influence of WC and titanium carbide (TiC) as secondary carbides on the tribological and machining behavior of NbC-12Ni-12WC-14TiC.

## 2. Methods

A NbC-12Ni-12WC-14TiC (vol%) cermet was produced through powder metallurgy techniques and supplied by BRATS LTDA, Cajamar, Brazil. In order to investigate the binder distribution, SEM-EDX investigations were performed. The tribological behavior was tested under dry oscillating sliding at room temperature and relative humidities of  $\varphi = 2, 50$  and  $98\%$ . The machining performance of the cermet was evaluated by dry external cylindrical turning of C45E at different cutting speeds.

## 3. Results

### 3.1. Tribological behavior

Figure 1 shows the wear rate  $k_{disk}$  of the C45E disk versus the coefficient of friction  $f$  of NbC, NbC-12Ni, NbC-12Ni-12WC-14TiC and WC-6Ni, which served as reference material after  $10^6$  cycles under dry, normal and moist conditions against a 100Cr6 ball. With increasing humidity,  $f$  and  $k_{disk}$  decrease.

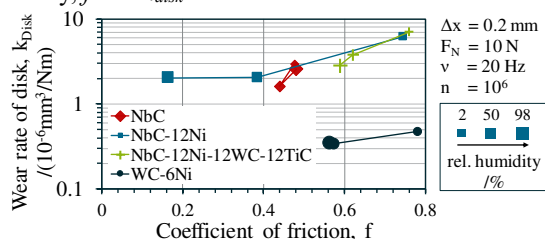


Figure 1: Wear rate  $k_{disk}$  versus coefficient of friction  $f$  under dry, normal and moist conditions against 100Cr6.

### 3.2. Machining behavior

Figure 2 shows the cutting performance of WC-6Co, (NbC-10TiC)-6Ni-7.5VC, NbC-12Ni-12WC-14TiC and

an industrially approved cermet TC60 from Kyocera in machining of C45E. Compared to WC-6Co, which shows a significant decrease in material removal  $V_w$  with increasing cutting speed,  $V_w$  of NbC-based cutting materials decrease less when high cutting speeds are used.

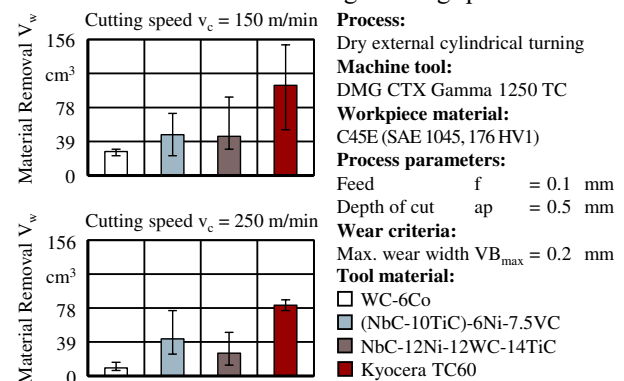


Figure 2: Comparison of material removal  $V_w$  of different cutting materials in machining of C45E.

## 4. Discussion

The microstructure of NbC-12Ni-12WC-14TiC is characterized by a large grain size distribution with grain sizes smaller than  $d = 5\ \mu\text{m}$  and a homogeneous distribution of Ni binder. It shows no improvement in  $f$  and  $k_{disk}$  compared to NbC and NbC-Ni. In machining of C45E, NbC-12Ni-12WC-14TiC demonstrates less material removal  $V_w$  compared to (NbC-10TiC)-6Ni-7.5VC and TC60. These findings can be attributed to inhomogeneities in the cutting material and the low hardness of  $1307 \pm 37\ \text{HV}_{30}$  in comparison to the other cutting materials. Further results will be reported in the final paper.

## 5. Acknowledgments

The authors thank the Deutsche Forschungsgemeinschaft (DFG) by project number 274971066 for the financial support.

## 6. References

- [1] Woydt, M. and Mohrbacher, H., "The tribological and mechanical properties of niobium carbides (NbC) bonded with cobalt or  $\text{Fe}_3\text{Al}$ ", *Wear*, 321, 2014, 1-7.
- [2] Huang, S. G. et al., "Microstructure and tribological performance of NbC-Ni cermets modified by VC and  $\text{Mo}_2\text{C}$ ", *Int J Refract Met H*, 66, 2017, 188-197.